

Virgin magnetization of a magnetically shielded superconductor wire: theory and experiment

Yu.A. Genenko* and S.V. Yampolskii†

Institut für Materialwissenschaft, Technische Universität Darmstadt, D-64287 Darmstadt, Germany

A.V. Pan

*Institute for Superconducting and Electronic Materials,
University of Wollongong, Wollongong, NSW 2522, Australia*

(Dated: February 2, 2008)

On the basis of exact solutions to the London equation, the magnetic moment of a type II superconductor filament surrounded by a soft-magnet environment is calculated and the procedure of extracting the superconductor contribution from magnetic measurements is suggested. Comparison of theoretical results with experiments on MgB₂/Fe wires allows estimation of the value of critical current for the first magnetic flux penetration.

PACS numbers: 74.25.Ha, 74.25.Sv, 41.20.Gz

Recently hybrid systems composed of superconducting and soft-magnetic materials attracted much attention in view of possibilities to improve superconductor performance by shielding out an external field as well as a transport current self-field^{1,2,3}. Very intense investigations were carried out on superconducting MgB₂ wires sheathed in iron, which became ideal objects to explore the magnetic shielding effect due to simplicity of their fabrication. As was observed in recent experiments, such structures exhibit enhanced superconducting critical currents over a wide range of the external magnetic field^{4,5}.

The commonly used technique for estimation of the critical current value is the measurement of superconductor magnetization versus applied magnetic field. Usually such measurements are carried out as follows^{5,6}. The total magnetization of MgB₂/Fe wire is measured in superconducting state (below T_c) and in normal state (above T_c). After that the magnetization of superconducting core is determined by subtraction of the latter results from the former ones (because in the normal state only magnetic sheath is magnetized). The magnetization of superconductor allows to estimate the critical current value which is proportional to the height of the hysteretic magnetic loop. It is assumed in this procedure that the magnetization of iron sheath does not depend on presence of superconductor and, hence, is identical above and below T_c . However, it is intuitively clear that this assumption may be somewhat incorrect. Indeed, due to the Meissner effect below T_c the superconductor expels the magnetic flux into the sheath. This expulsion does not happen in the normal state where the magnetic field is homogeneous in the cylindrical magnetically shielded cavity⁷. Therefore, the magnetic field distribution in the magnet sheath as well as its magnetization can be different, depending on whether the core is in the superconducting state or in the normal one. Recently, this scenario has been supported by magneto-optical visualization of local flux distributions within the iron sheath of MgB₂ superconducting wire⁸.

In the present Letter we calculate exactly the distribution of magnetic field inside and outside a superconducting filament sheathed by a magnet layer, as well as the magnetization of such structure in the region of reversible magnetic behavior, i.e. for the flux-free (Meissner) state of the superconductor and well below the saturation field of the magnet. Comparing theoretical results with experiment we verify the above described procedure of the superconducting critical current estimation.

Let us consider an infinite cylindrical superconductor filament of radius R enveloped in a coaxial cylindrical magnetic sheath of thickness d with relative permeability μ and exposed to the external magnetic field $\mathbf{H}_0$ perpendicular to the cylinder axis (Fig. 1).

We start from the London equation for the magnetic induction $\mathbf{B}_{SC}$ in the superconducting area⁹

$$\mathbf{B}_{SC} + \lambda^2 \text{curl curl } \mathbf{B}_{SC} = 0, \quad (1)$$

with the London penetration depth λ . The field outside the superconductor denoted by $\mathbf{H}_M$ in a magnetic sheath and by $\mathbf{H}_{out}$ in a surrounding free space is described by the Maxwell equations

$$\text{curl } \mathbf{H} = 0, \quad \text{div } \mathbf{H} = 0, \quad (2)$$

the latter of which is valid in the whole space. Implying an insulating, nonmagnetic layer of thickness much less than d and R between the superconductor and the magnet sheath¹⁰ the boundary conditions read

$$B_{n,SC} = \mu_0 \mu H_{n,M}, \quad B_{t,SC} = \mu_0 H_{t,M}; \quad (3a)$$

$$\mu H_{n,M} = H_{n,out}, \quad H_{t,M} = H_{t,out}, \quad (3b)$$

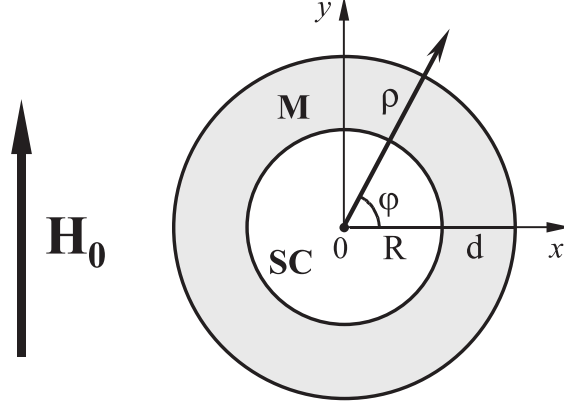


FIG. 1: Cross-sectional view of a superconductor filament covered by a coaxial cylindrical magnetic sheath.

for the normal (n) and tangential (t) components on the superconductor/magnet interface (Eq. (3a)) and on the outer magnet surface (Eq. (3b)), respectively. In addition, the field $\mathbf{H}_{out}$ has to approach asymptotically the external field $\mathbf{H}_0$. In cylindrical coordinates (ρ, φ, z) coaxial with the filament the solution of Eqs. (1-2) is:

$$\begin{aligned} B_{\rho, SC} &= \mu_0 H_0 A_{SC} [I_0(\rho/\lambda) - I_2(\rho/\lambda)] \sin \varphi, \\ B_{\varphi, SC} &= \mu_0 H_0 A_{SC} [I_0(\rho/\lambda) + I_2(\rho/\lambda)] \cos \varphi, \end{aligned} \quad (4)$$

in the superconductor;

$$\begin{aligned} H_{\rho, M} &= H_0 (A_{M1} - A_{M2} R^2 / \rho^2) \sin \varphi, \\ H_{\varphi, M} &= H_0 (A_{M1} + A_{M2} R^2 / \rho^2) \cos \varphi, \end{aligned} \quad (5)$$

in the magnet sheath; and

$$\begin{aligned} H_{\rho, out} &= H_0 \left[1 + A_{out} (R + d)^2 / \rho^2 \right] \sin \varphi, \\ H_{\varphi, out} &= H_0 \left[1 - A_{out} (R + d)^2 / \rho^2 \right] \cos \varphi, \end{aligned} \quad (6)$$

in the space around the filament. The coefficients A_{SC} , A_{M1} , A_{M2} and A_{out} are given by expressions

$$\begin{aligned} A_{SC} &= 4\mu/\Delta, \\ A_{M1} &= 2[(\mu + 1) I_0(R/\lambda) + (\mu - 1) I_2(R/\lambda)] / \Delta, \\ A_{M2} &= 2[(\mu - 1) I_0(R/\lambda) + (\mu + 1) I_2(R/\lambda)] / \Delta, \\ A_{out} &= \left\{ \left[(\mu - 1)^2 - (\mu + 1)^2 R^2 / (R + d)^2 \right] I_2(R/\lambda) \right. \\ &\quad \left. + (\mu^2 - 1) \left[1 - R^2 / (R + d)^2 \right] I_0(R/\lambda) \right\} / \Delta, \end{aligned} \quad (7)$$

where

$$\begin{aligned} \Delta &= \left[(\mu + 1)^2 - (\mu - 1)^2 R^2 / (R + d)^2 \right] I_0(R/\lambda) \\ &\quad + (\mu^2 - 1) \left[1 - R^2 / (R + d)^2 \right] I_2(R/\lambda). \end{aligned} \quad (8)$$

The Meissner current density in the superconductor has only z -component which equals

$$j_z(\rho, \varphi) = A_{SC} \frac{2H_0}{\lambda} I_1(\rho/\lambda) \cos \varphi. \quad (9)$$

A limiting case of the hollow magnetic cylinder may be obtained from Eqs. (4-8) by setting $\lambda \rightarrow \infty$ which results in a nonzero homogeneous field inside the hole as expected from Ref.⁷.

Now we can easily calculate the mean magnetization of both superconducting core and iron sheath which, due to the geometry of the problem, has only y -component. The magnetization of the superconductor is

$$M_{SC} = \frac{1}{V_{SC}} \int_{V_{SC}} dV [\vec{\rho} \times \vec{j}]_y = -2A_{SC}H_0I_2(R/\lambda), \quad (10)$$

where the factor 2 is due to account for the far ends of the sample¹¹. The magnetization of the iron sheath is

$$M_M = \frac{\mu - 1}{V_M} \int_{V_M} dV H_{y,M} = (\mu - 1) H_0 A_{M1}. \quad (11)$$

In the practically interesting case $R \gg \lambda$ they become

$$M_{SC} \simeq -\frac{4H_0}{\mu + 1 - (\mu - 1)/(1 + d/R)^2}, \quad (12)$$

$$M_M \simeq \frac{2(\mu - 1)H_0}{\mu + 1 - (\mu - 1)/(1 + d/R)^2}. \quad (13)$$

Although the magnetization of the sheath (13) does not contain λ it does not coincide with the magnetization of a hollow magnetic cylinder which can be obtained from Eq. (11) by setting $\lambda \rightarrow \infty$:

$$M_{HC} \simeq \frac{2(\mu^2 - 1)H_0}{(\mu + 1)^2 - (\mu - 1)^2/(1 + d/R)^2}. \quad (14)$$

For the ratio of these two quantities an inequality

$$\frac{M_M}{M_{HC}} = \frac{(\mu + 1)^2 - (\mu - 1)^2/(1 + d/R)^2}{(\mu + 1)^2 - (\mu^2 - 1)/(1 + d/R)^2} > 1 \quad (15)$$

holds which means the magnetic flux density increase due to the flux expelled from the superconductor.

Although in the critical state of superconductors only part of the magnetic flux is expelled, the same inequality $M_M > M_{HC}$ should be still valid. Therefore, we conclude that in previous considerations^{4,5,6} the magnetization of the sheath below T_c could be underestimated and, hence, the magnetization of a superconductor together with the critical current value could be underestimated too.

Note that slopes of both magnetizations (13) and (14), $M_{M(HC)}/H_0$, have *finite* values at any fixed parameter d/R even in the limit of $\mu \rightarrow \infty$. It differs from the case of the field parallel to the filament axis, when the shielding effect is absent for an infinitely long cylinder sheath⁷ and the corresponding slope $M_{M(HC)}/H_0 = \mu - 1$ rises unbounded with μ . In fact, the shielding effect of a much smaller amplitude was also observed in the longitudinal geometry due to the finite length of samples^{4,10}.

Now we use the theoretical expressions to fit experimental results. Details of the sample preparation and measurement technique were given in Ref.⁵. The sample had the length of $L = 4.1$ mm, the radius of the superconducting core $R = 0.5$ mm, the magnet sheath thickness $d = 0.25$ mm, and the permeability $\mu = 46$ measured in the longitudinal field¹⁰. The difference between magnetic moments measured in the normal and in the superconducting states was quite small (about 1%) at fields $B_0 = \mu_0 H_0 < 0.1$ T (see Fig. 2). The magnetic moment in the normal state was fitted using M_{HC} (14) while the total moment below T_c was fitted using M_{SC} (12) and M_M (13) with the only fitting parameter of ratio η between the effective lengths of magnetic sheath and superconductor. The best fit was achieved for $\eta = 1.5$. The deviation of η from 1 indicates the significant role of the sample edge effects leading to the discrepancy between the measured magnetic moment of the relatively short sample and the moment calculated for an infinitely long cylinder with Eqs. (12-14).

Using the above parameters we calculate the $M_M(B_0)$ dependence in the superconducting state from Eq. (13) which is shown in Fig. 2 by the dash-dotted line. From Eqs. (13-14) it follows that the magnetization of the iron sheath at $T < T_c$ is about 3% larger than that at $T > T_c$. Let us note that this difference may reach 100% at smaller values of the parameters d/R and μ .

The response of the magnetic sheath is intrinsically nonlinear that is clearly visible in the normal state magnetization curve at $B_0 > 0.15$ T. The deviation of the total magnetic moment below T_c at $B_p \simeq 0.3$ T from that in the normal state may be attributed to the nonlinearity due to the first magnetic flux entry into the superconductor. From the B_p value a critical current of the first vortex penetration may be estimated as follows.

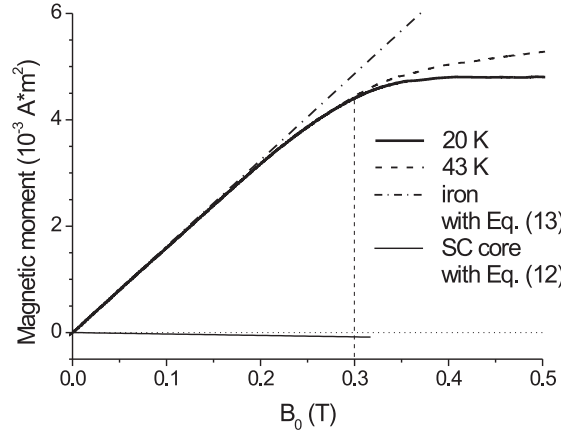


FIG. 2: The magnetic moment dependence of the MgB₂/Fe wire on the magnetic field applied transversely in the superconducting state (thick solid line) and in the normal state (dashed line). The moment of the iron sheath in the superconducting state calculated using Eq. (13) is presented by the dash-dotted line. The thin solid line exhibits the superconductor core contribution.

First, from the magnetization of the superconducting core the maximum value of screening current $j_s = j_z(R, 0)$ can be found. Combining Eqs. (9)-(10) we obtain in the case $R \gg \lambda$

$$j_s \simeq 2 |M_{SC}| / \lambda, \quad (16)$$

with M_{SC} from Eq. (12). Taking $\mu = 46$, $d/R = 0.5$ and $\lambda = 1400 \text{ \AA}$ for $T = 30 \text{ K}$ from Ref.¹² we obtain for $H_0 = B_p/\mu_0$ the value of $j_s \simeq 5 \times 10^7 \text{ A/cm}^2$. A practically important quantity is the average density of the screening current that may be defined as $j_c = 2J_c/\pi R^2$ where J_c is determined by the integration of expression (9) over the half of the superconductor cross-section. In the limit of $R \gg \lambda$ we obtain

$$j_c \simeq 8 |M_{SC}| / \pi R, \quad (17)$$

and for the parameters used we found $j_c \simeq 1.8 \times 10^4 \text{ A/cm}^2$ which is in a good agreement with the results of Refs.^{4,5,10}.

In conclusion, we have developed a procedure of extracting the superconducting response from the low field magnetic measurements on the iron sheathed superconductor filaments taking into account the difference between the magnetization of the magnet sheath below and above T_c .

Discussions of boundary conditions with A. Gurevich are gratefully acknowledged. This study was supported by the Deutsche Forschungsgemeinschaft (S.V.Y.) and by the Australian Research Council (A.V.P.).

* Electronic address: yugen@tgm.tu-darmstadt.de

† On leave from Donetsk Institute for Physics and Technology, National Academy of Sciences of Ukraine, 83114 Donetsk, Ukraine.

¹ M. Majoros, B.A. Glowacki, and A.M. Campbell, *Physica C* **334**, 129 (2000); **338**, 251 (2000).

² Yu.A. Genenko, A. Usoskin, and H.C. Freyhardt, *Phys. Rev. Lett.* **83**, 3045 (1999); Yu.A. Genenko, A. Snezhko, and H.C. Freyhardt, *Phys. Rev. B* **62**, 3453 (2000).

³ H. Jarzina, Ch. Jooss, and H.C. Freyhardt, *J. Appl. Phys.* **91**, 3775 (2002).

⁴ J. Horvat, X.L. Wang, S. Soltanian, and S.X. Dou, *Appl. Phys. Lett.* **80**, 829 (2002).

⁵ A.V. Pan, S.H. Zhou, H.K. Liu, and S.X. Dou, *Supercond. Sci. Technol.* **16**, L33 (2003).

⁶ M.D. Sumption, E.W. Collins, E. Lee, X.L. Wang, S. Soltanian, and S.X. Dou, *Physica C* **378**, 894 (2002).

⁷ J.D. Jackson, *Classical electrodynamics* (Wiley, New York, 1975).

⁸ A.V. Pan, S.X. Dou, and T.H. Johansen, *Proc. of NATO Advanced Research Workshop on Magneto-Optical Imaging, Øystese, Norway* (2003) (in press).

⁹ P.G. de Gennes, *Superconductivity of Metals and Alloys* (Addison-Wesley, New York, 1994).

¹⁰ A.V. Pan and S.X. Dou (2003), unpublished.

¹¹ E.H. Brandt and M. Indenbom, *Phys. Rev. B* **48**, 12893 (1993).

¹² P.C. Canfield, S.L. Bud'ko, and D.K. Finnemore, *Physica C* **385**, 1 (2003).